

STEEL GRADE

Last revised: Fri, 17 Jan 2025 10:22:04 GMT

20NiCrMo2-2 All

General Information

Ovako 152 is a high cleanliness case hardening steel used for bearing, transmission components and other highly stressed applications. There are three versions of the grade.

152A / 20NiCrMoS2 - variant with regulated sulphur content for enhanced machinability

152C / 20NiCrMo2 - variant with enhanced hardenability (BQ)

152G / 20NiCrMo2 - Bearing Steel Quality (BQ) variant

BQ-Steel®

BQ-Steel® is a bearing quality clean steel optimized for fatigue strength and is also ideal for new design solutions outside the bearing industry.

Similar designations

20NiCrMo2, 20NiCrMoS2, 8620, 8620H, 1.6522, 1.6523, 1.6526, SS2506, UNS H 86200

Chemical composition

Variant	Cast	DI	Weldability		C %	Si %	Mn %	P %	S %	Cr %	Ni %	Mo %
152A	IC		CEV 0.65 _{max}	Min	0.18	0.20	0.65	-	0.015	0.40	0.40	0.15
			Pcm 0.38 _{max}	Max	0.23	0.35	0.90	0.025	0.035	0.70	0.70	0.25
152C	IC	2.21	CEV 0.63 _{max}	Min	0.21	0.25	0.84	-	0.008	0.56	0.55	0.18
			Pcm 0.37 _{max}	Max	0.23	0.35	0.90	0.025	0.015	0.60	0.60	0.21
152G	IC		CEV 0.64 _{max}	Min	0.19	0.20	0.70	-	0.008	0.40	0.40	0.15
			Pcm 0.37 _{max}	Max	0.23	0.35	0.90	0.015	0.015	0.60	0.70	0.25
20NiCrMo2-2 +H EN ISO 683-3	Std		CEV _{max}	Min	0.17	-	0.65	-	0.020	0.35	0.40	0.15
			Pcm _{max}	Max	0.23	0.40	0.95	0.025	0.040	0.70	0.70	0.25

152C : DI min 2,21.

Mechanical Properties

Variant	Condition	Format	Dimension [mm]	Hardness
152A	+AR	Round bar	40 < 80	230 HB typical
	+A	Round bar	40 < 80	212 HB typical
152G	+AR	Round bar	40 < 70	230 HB typical
	+A	Round bar	40 < 70	212 HB typical

$R_{p0.2}$ * R_{eh} ** R_{el}

Transformation temperatures

	Temperature °C
MS	405
AC1	723
AC3	812


Heat treatment recommendations

Treatment	Condition	Temperature cycle	Cooling/quenching
Hot forging	+U	800-1200C	In air
Normalizing	+N	860-890C	In air
Soft annealing	+SA	600-670 2h	In air
Carburizing	+C	850-930C Carbon potential see diagram	
Quench & Tempering	+QT	Q/T 840-890C Hardening of as-carburized component 780-830C	In oil
Tempering	+T	160-250C	In air


Heat Treatment Guide generated Graphs

The following graphs are generated from a theoretical model. For further info see the Heat treatment guide module. Select a specific grade version for individual display.


Tempering Diagram (hardness)

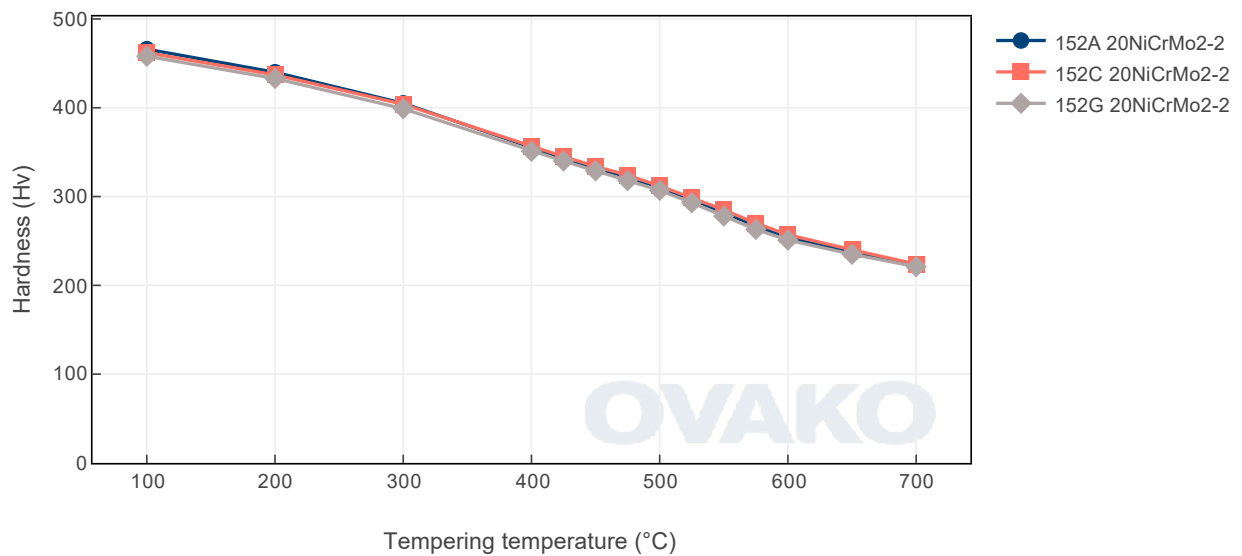


Tempering Diagram (strength)

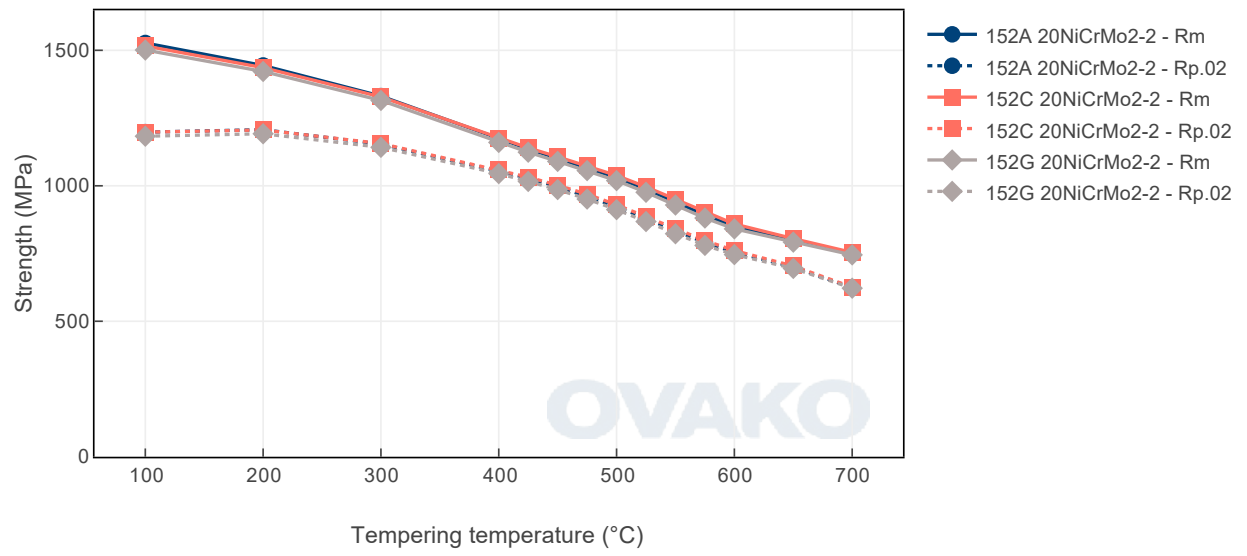

Jominy


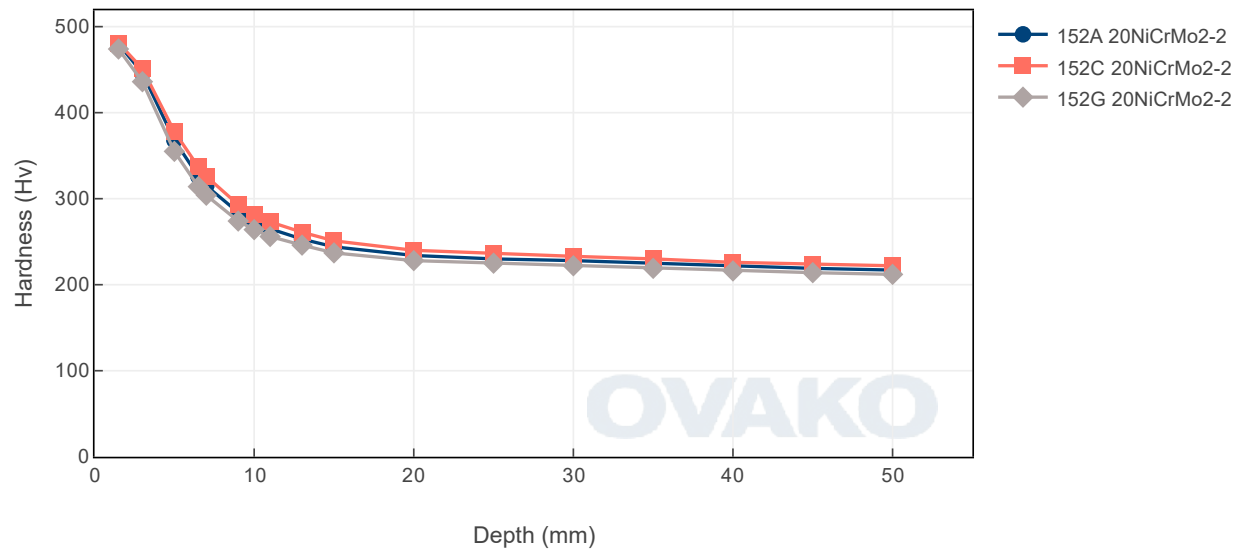


Hardenability

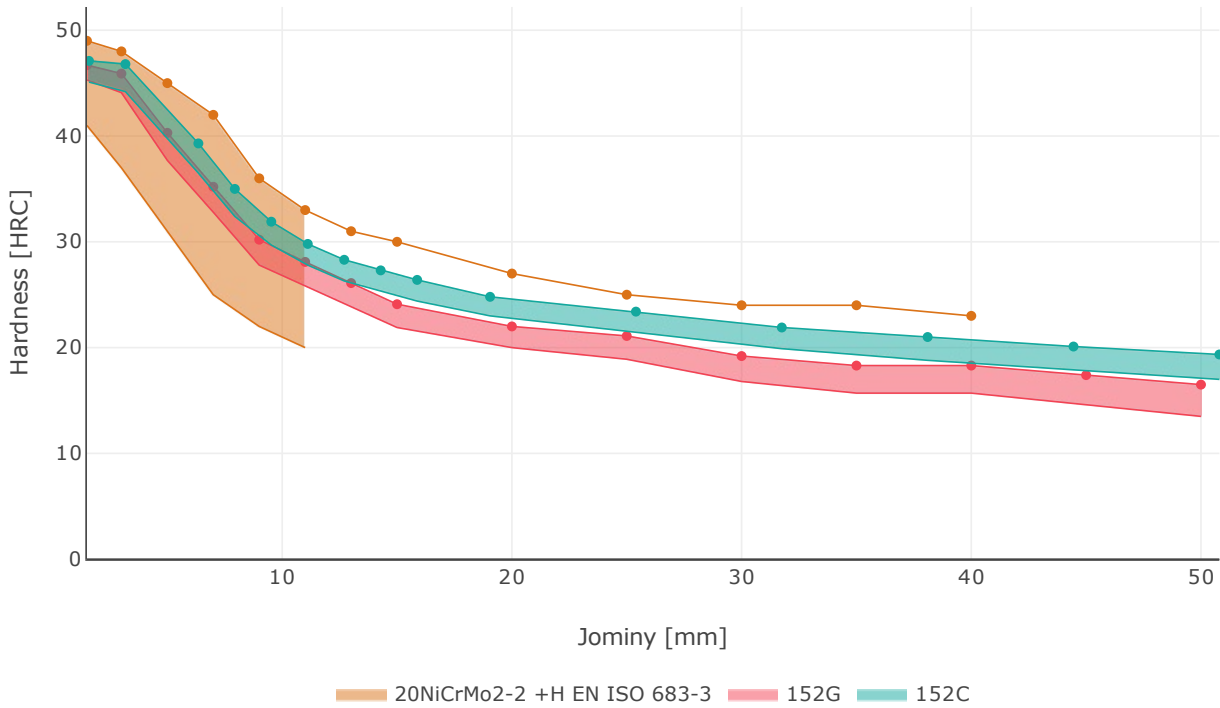

20NiCrMo2-2+H shows the Jominy band according to EN ISO 683-3. Jominy hardenability according to ASTM A255. The graph also shows the average values +/- 1 standard deviation for steel grade 152G and 152C.

Carburizing response - Ovako 152G

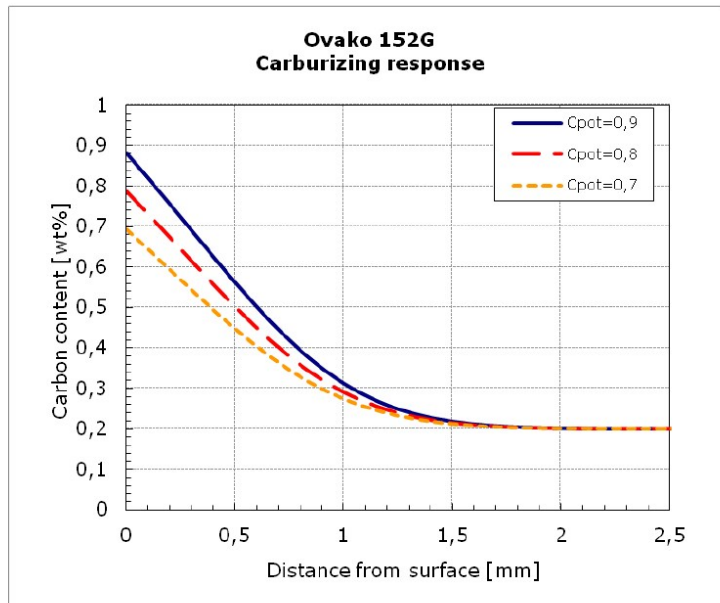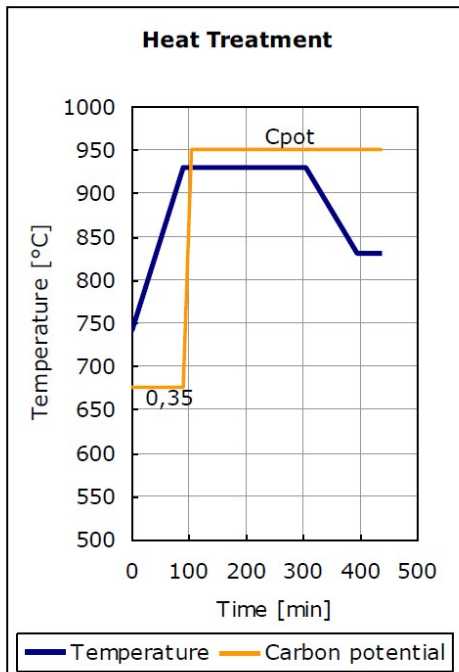

Carburization response for Ovako 152G for the cycles shown in the left figure. Response of 152A and 152C similar.

SUSTAINABILITY-ENVIRONMENTAL IMPACT DATA

At Ovako sustainability and reduction of our environmental impact is a major focus in everything we do.

Further information is found [here](#).

Steel works	Hofors	Smedjebacken	Imatra
CO2e/kg	120	62	76

To get the full picture of our products environmental impact we have to look at all of our CO₂ emission sources.

Not only the steel work Scope 1-2 itself, but all operations downstream in our production, heating and heat treatment furnaces etc (full scope 1-2) as well as all the emission from input material, eg. alloys, scope 3.

Steel Grade	Format	Condition	Scope 1-3 (CO2e kg /1000 kg steel)
152	Round bar	+AR	676
152	Round bar	+FP	681
152	Tube,wall	+AR	704
152	Tube,wall	+FP	707
4542	Round bar	+AR	593
4532	Round bar	+AR	593
4548, MoCN 206 M	Round bar	+AR	584

To get the full picture of our products environmental impact we have to look at all of our CO₂ emission sources.

Not only the steel work Scope 1-2 itself, but all operations downstream in our production, heating and heat treatment furnaces etc (full scope 1-2) as well as all the emission from input material, eg. alloys, scope 3.

Other properties (typical values)

Youngs module (GPa)	Poisson´s ratio (-)	Shear module (GPa)	Density (kg/m ³)
210	0.3	80	7800
Average CTE 20-300°C (µm/m°K)	Specific heat capacity 50/100°C (J/kg °K)	Thermal conductivity Ambient temperature (W/m°K)	Electrical resistivity Ambient temperature (µΩm)
12	460 - 480	40 - 45	0.20 - 0.25

Contact us

Would you like to know more about our offers? Don´t hesitate to contact us:

Via e-mail: info@ovako.com

Via telephone: +46 8 622 1300

For more detailed information please visit <http://www.ovako.com/en/Contact-Ovako/>

Disclaimer

The information in this document is for illustrative purposes only. The data and examples are only general recommendations and not a warranty or a guarantee. The suitability of a product for a specific application can be confirmed only by Ovako once given the actual conditions. The purchaser of an Ovako product has the responsibility to ascertain and control the applicability of the products before using them. Continuous development may necessitate changes in technical data without notice. This document is only valid for Ovako material. Other material, covering the same international specifications, does not necessarily comply with the properties presented in this document.