

STEEL GRADE

Last revised: Thu, 30 Jan 2025 11:22:11 GMT

52CrMoV4 All

General Information

52CrMoV4 is a springsteel suitable for quenching and tempering, used in e.g. leaf springs and other vehicle springs.

Similar designations

SB9296 - 54CrMnMo4-4, 51CrMoV4

Chemical composition

Variant	Cast	DI	Weldability		C %	Si %	Mn %	P %	S %	Cr %	Ni %	Mo %	V %	Ti %	Cu %
596A	IC		CEV _{max}	Min	0.48	0.15	0.70	-	-	0.90	-	0.15	0.100	-	-
			Pcm _{max}	Max	0.56	0.40	1.10	0.025	0.008	1.20	0.30	0.30	0.200	-	-
SB9296	CC	8.4	CEV 1.01 _{max}	Min	0.51	0.25	0.94	-	-	1.02	-	0.15	0.100	-	-
			Pcm 0.7 _{max}	Max	0.56	0.40	1.10	0.015	0.015	1.12	0.20	0.20	0.120	0.040	0.21
52CrMoV4 EN10089:2002	Std		CEV _{max}	Min	0.48	-	0.70	0.000	0.000	0.90	-	0.15	0.100	-	-
			Pcm _{max}	Max	0.56	0.40	1.10	0.025	0.025	1.20	-	0.30	0.200	-	-

Mechanical Properties

Variant	Condition ⁱ	Format	Dimension [mm]	Yield strength min [MPa]	Tensile strength [MPa]	Elongation A ₅ [%]	Reduction of area Z _{min} [%]	Hardness	Impact (ISO-V) strength _{min}
SB9296	+AR	All formats	-	-	-	-	-	< 440 HB	-
		Flat bar	9 < 30	-	-	-	-	381 HB typical	-
		Flat bar	30 < 56	-	-	-	-	345 HB typical	-
		Round bar	30 < 50	-	-	-	-	353 HB typical	-
		Round bar	50 < 95	-	-	-	-	346 HB typical	-
52CrMoV4 EN10089:2002	+S	All formats	-	-	-	-	-	< 280 HB	-
	+A	All formats	-	-	-	-	-	< 248 HB	-
	+AC	All formats	-	-	-	-	-	< 230 HB	-
	+QT	All formats	-	1300	1450-1750	6	35	-	20 °C 10 J (long)

*R_{p0.2} * R_{eh} ** R_{el}*

Impact test is made with U-notched pieces in +QT.

Reference treatment for 52CrMoV4 EN10089:2002 is quench from 860 °C followed by tempering at 450 °C.


Transformation temperatures

	Temperature °C
MS	265
AC1	737
AC3	776


Heat Treatment Guide generated Graphs

The following graphs are generated from a theoretical model. For further info see the Heat treatment guide module. Select a specific grade version for individual display.


Tempering Diagram (hardness)

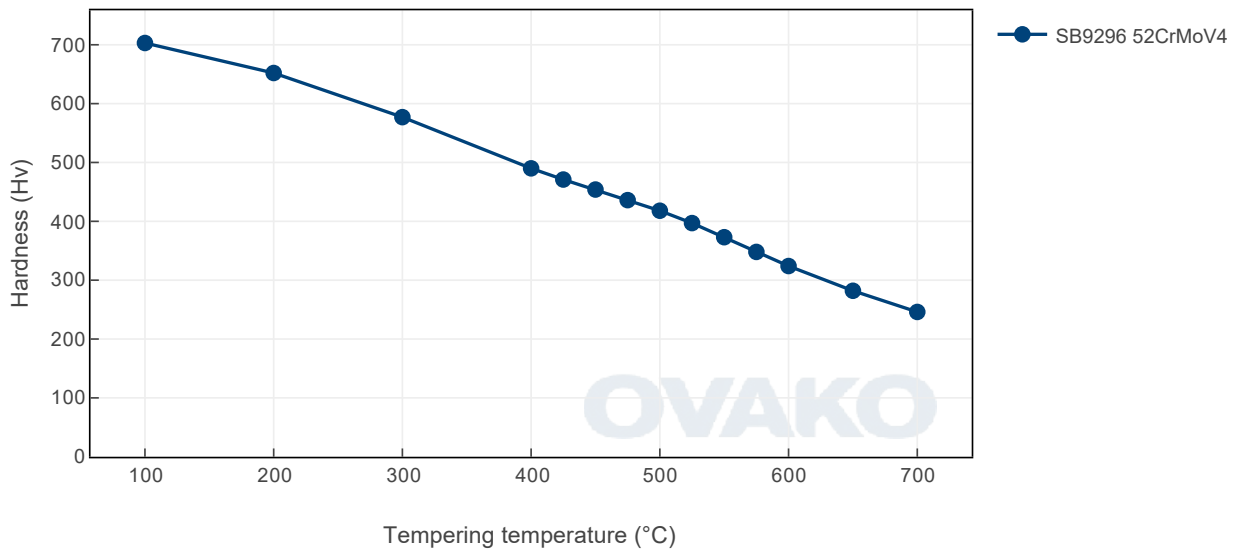


Tempering Diagram (strength)

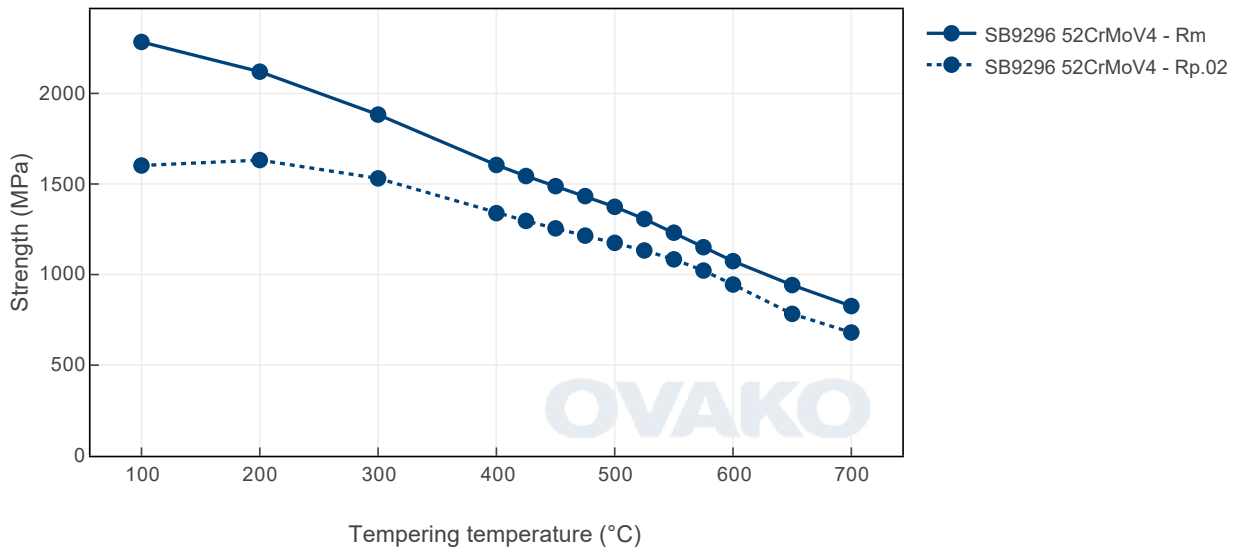

Jominy

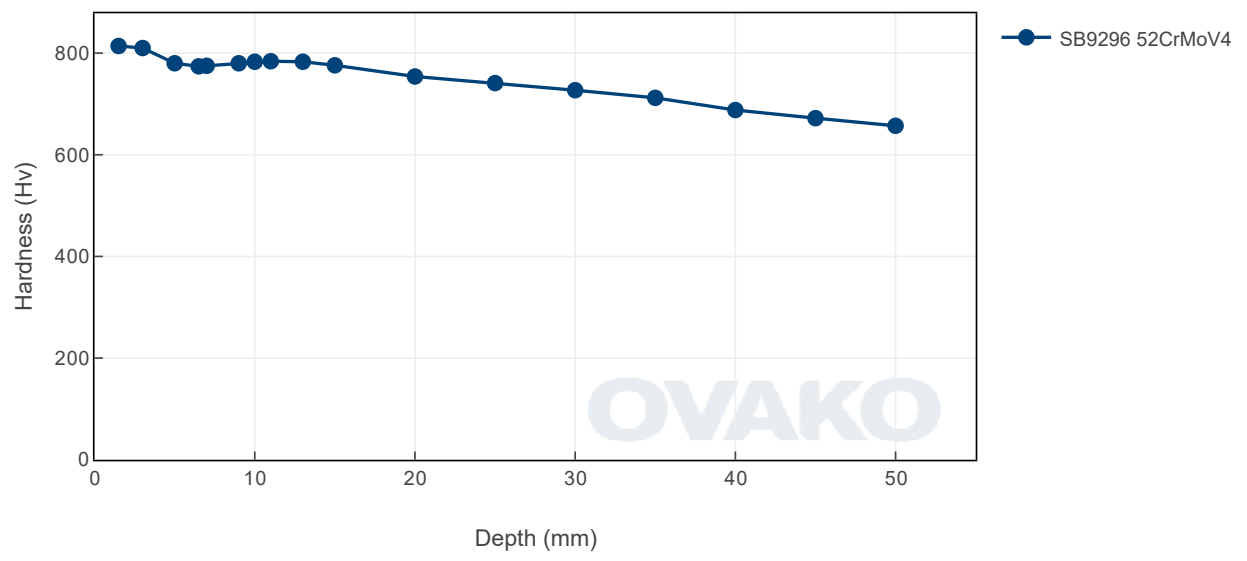

Hardenability

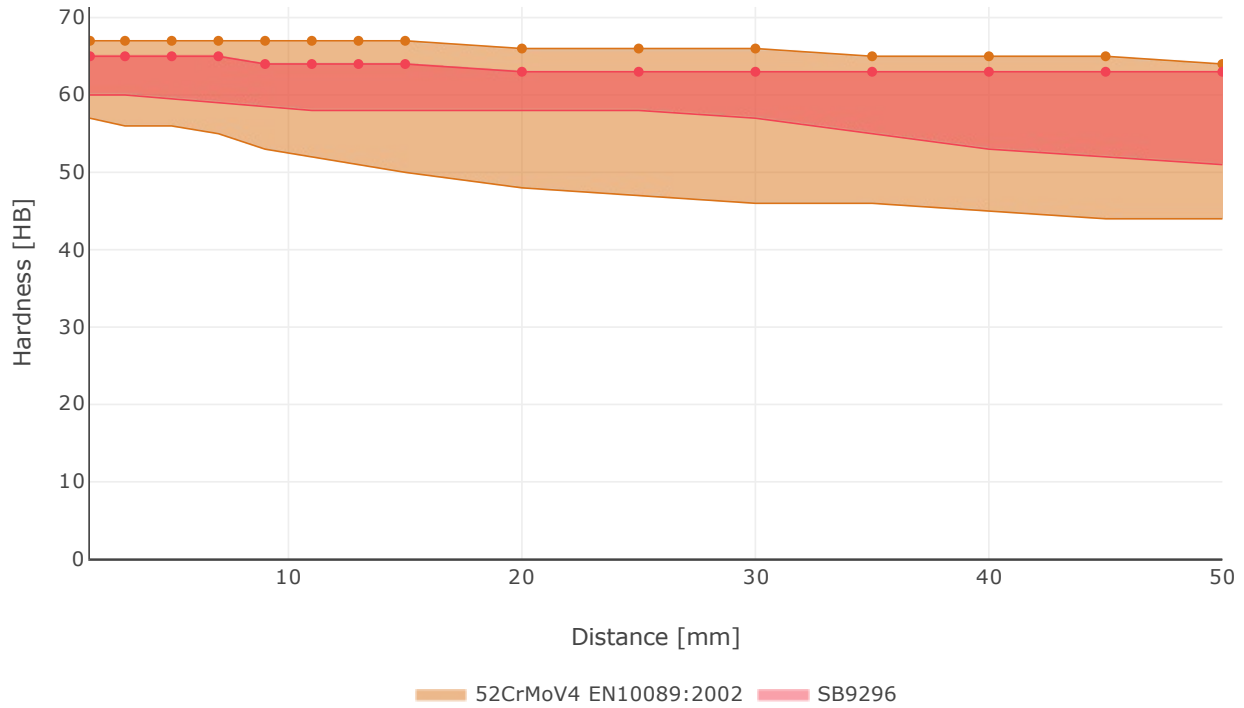

SUSTAINABILITY-ENVIRONMENTAL IMPACT DATA

At Ovako sustainability and reduction of our environmental impact is a major focus in everything we do.

Further information is found [here](#).

Steel works	Hofors	Smedjebacken	Imatra
CO ₂ e/kg	120	62	76

To get the full picture of our products environmental impact we have to look at all of our CO₂ emission sources.

Not only the steel work Scope 1-2 itself, but all operations downstream in our production, heating and heat treatment furnaces etc (full scope 1-2) as well as all the emission from input material, eg. alloys, scope 3.

Steel Grade	Format	Condition	Scope 1-3 (CO ₂ e kg /1000 kg steel)
SB9296	Flat bar	+AR	454

All above data are to be seen as typical values for the specified format and condition. Detailed information about your specific product please contact your sales contact.

Other properties (typical values)

Youngs module (GPa)	Poisson 's ratio (-)	Shear module (GPa)	Density (kg/m ³)
210	0.3	80	7800
Average CTE 20-300°C (µm/m°K)	Specific heat capacity 50/100°C (J/kg °K)	Thermal conductivity Ambient temperature (W/m°K)	Electrical resistivity Ambient temperature (µΩm)
12	460 - 480	40 - 45	0.20 - 0.25

Contact us

Would you like to know more about our offers? Don't hesitate to contact us:

Via e-mail: info@ovako.com

Via telephone: +46 8 622 1300

For more detailed information please visit <http://www.ovako.com/en/Contact-Ovako/>

Disclaimer

The information in this document is for illustrative purposes only. The data and examples are only general recommendations and not a warranty or a guarantee. The suitability of a product for a specific application can be confirmed only by Ovako once given the actual conditions. The purchaser of an Ovako product has the responsibility to ascertain and control the applicability of the products before using them. Continuous development may necessitate changes in technical data without notice. This document is only valid for Ovako material. Other material, covering the same international specifications, does not necessarily comply with the properties presented in this document.