

94CrMo5-2* All

General Information

Ovako 821L is a through hardening bearing steel intended for rolling contact and other high fatigued applications. In the hardened condition the high hardness, high strength and high cleanliness provides the steel with the right properties to withstand high cycle, high stress fatigue. Ovako 821L is mainly used for small and medium sized bearing components. It is also regularly used for other machine components that require high tensile strength and high hardness.

** Designation followed by “ * ” is not an official EN standard grade but named according to the rules in EN 10027.”*

BQ-Steel®

BQ-Steel® is a bearing quality clean steel optimized for fatigue strength and is also ideal for new design solutions outside the bearing industry.

Similar designations

100Cr6, 52100, 100 C 6

Chemical composition

Variant	Cast		C %	Si %	Mn %	P %	S %	Cr %	Ni %	Mo %
821L	IC	Min	0.94	0.10	0.25	-	-	1.30	-	0.20
		Max	1.00	0.15	0.45	0.015	0.010	1.50	0.15	0.23

Mechanical Properties

Variant	Condition ⁱ	Format	Yield strength min [MPa]	Tensile strength [MPa]	Elongation A ₅ [%]	Hardness
821L	+SA	All formats	410	700 typical	27	195 HB typical
	+C	All formats	700	880 typical	13	290 HB typical
	+Q/T(m)	All formats	1700	2300 typical	2	61 HRC typical
	+Q/T(b)	All formats	2000	2200 typical	7	59 HRC typical

*RP_{0.2} * R_{eh}, ** R_{el}*

Transformation temperatures

	Temperature °C
MS	115
AC1	750
AC3	750


Heat treatment recommendations

Treatment	Condition ⁱ	Temperature cycle	Cooling/quenching
Hot forging	+U	800-1100°C	In air
Spheroidize annealing	+SA	RT-820°C 1h, 820°C 2h, 820-740°C 1h, 740-690°C 10h	In air
Stress relieve annealing	+SRA	550-650°C	In air
Tempering	+T	160-500°C (see diagram)	In air
Q/T (martensite)	+Q/T(m)	830-870°C 10-60min	In oil (tempering within 2h) see diagram
Q/T (bainite)	+Q/T(b)	850-875°C 10-60min	Salt bath 220-250°C 3-7h (see diagram)


Heat Treatment Guide generated Graphs

The following graphs are generated from a theoretical model. For further info see the Heat treatment guide module. Select a specific grade version for individual display.


Tempering Diagram (hardness)

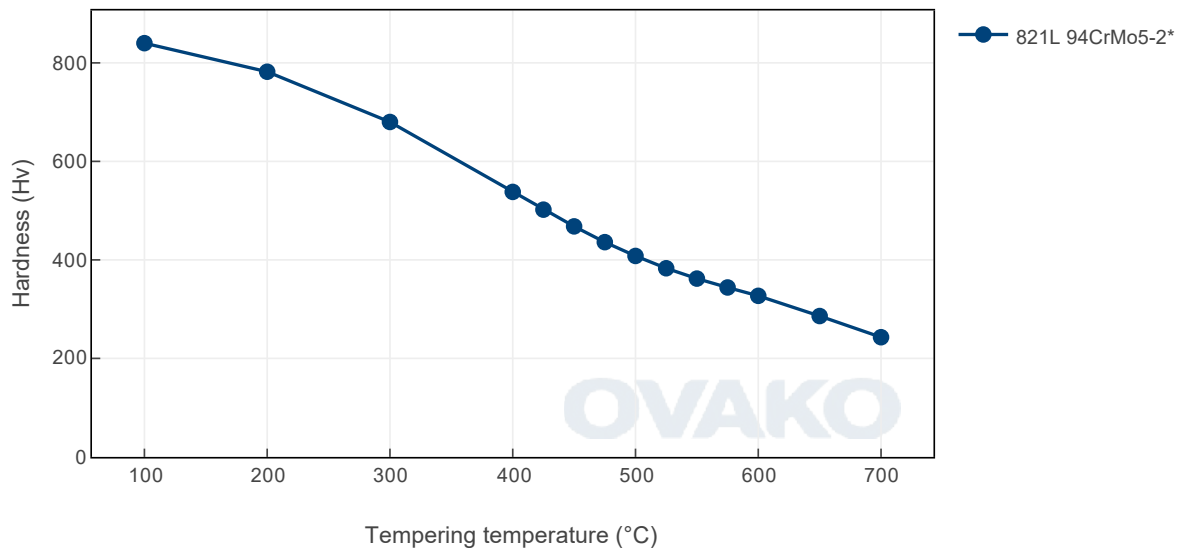


Tempering Diagram (strength)

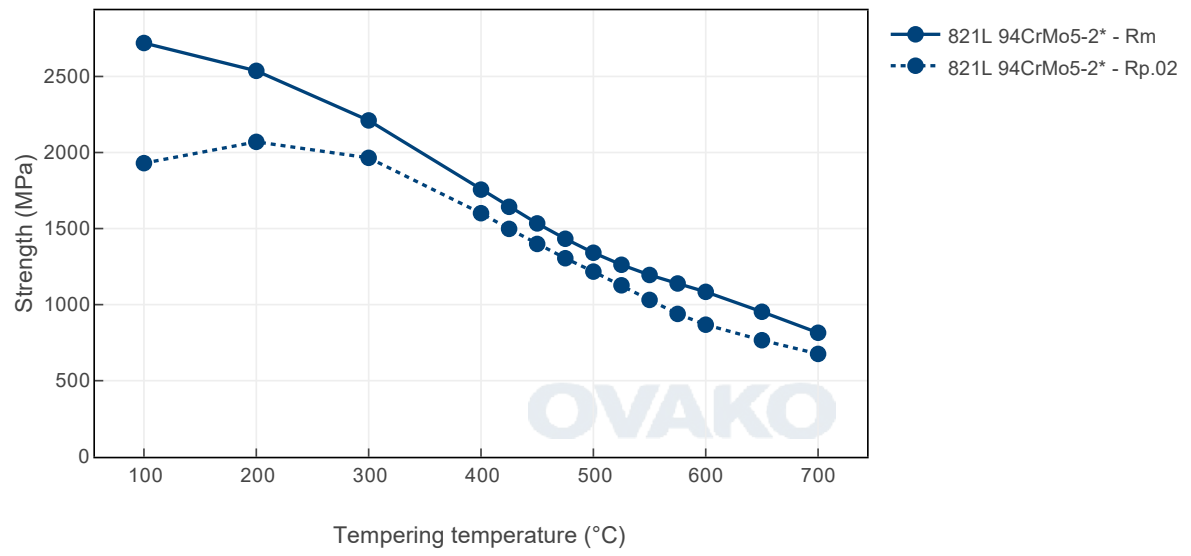

Jominy

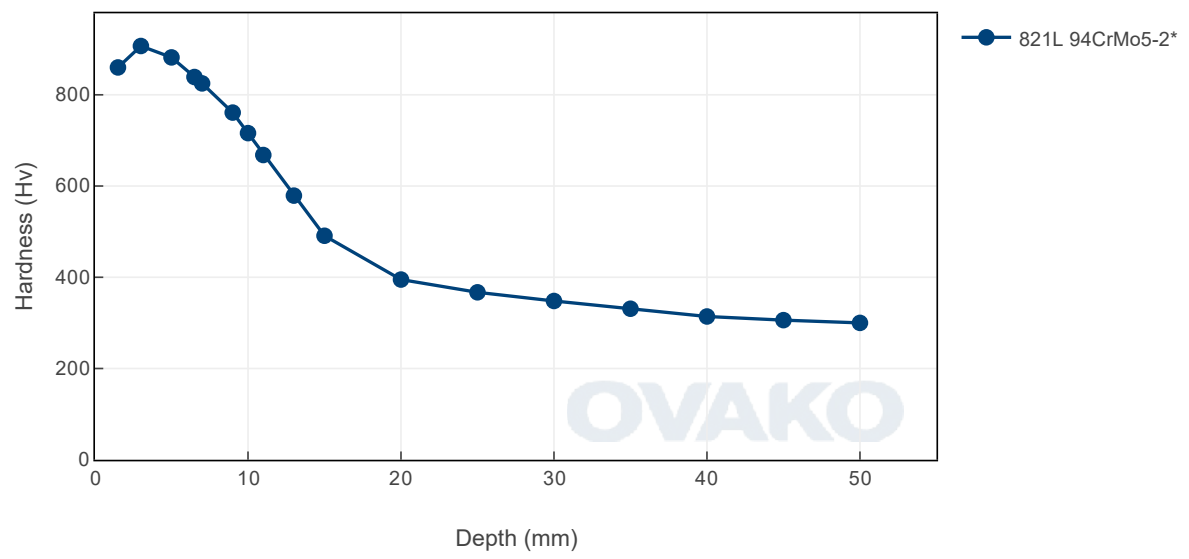


Hardenability

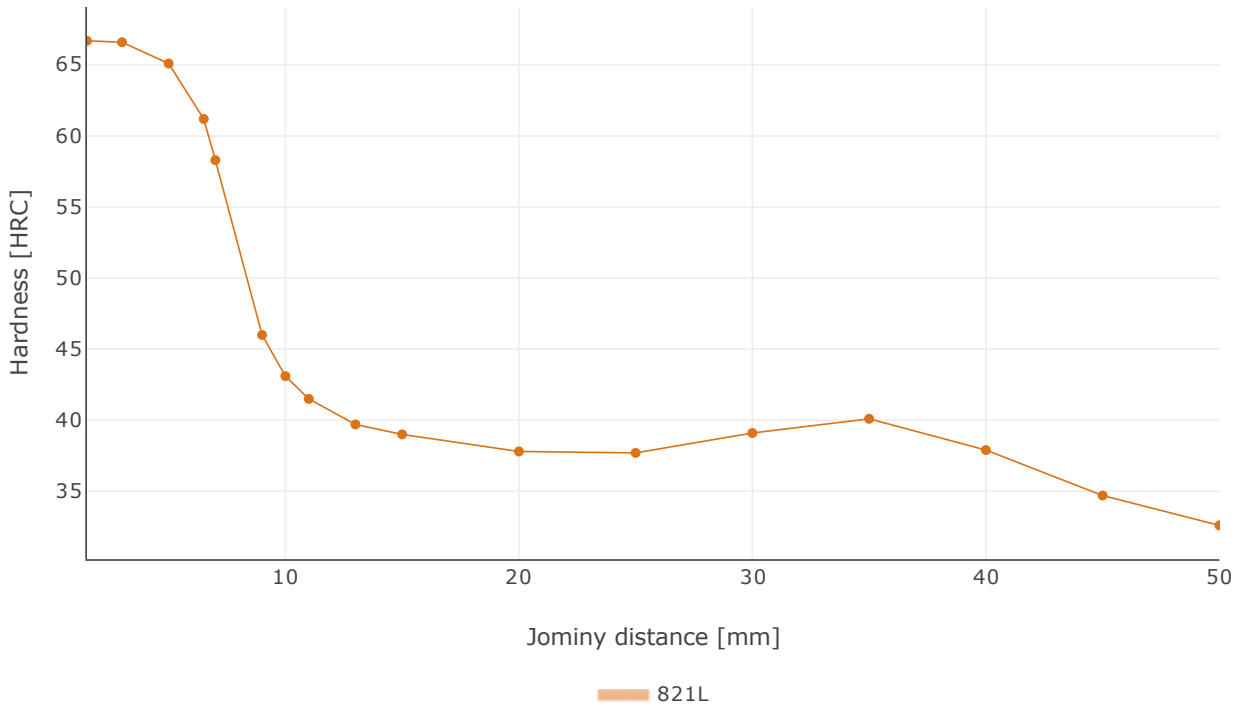

Average value. Austenitized at 845°C

Tempering response

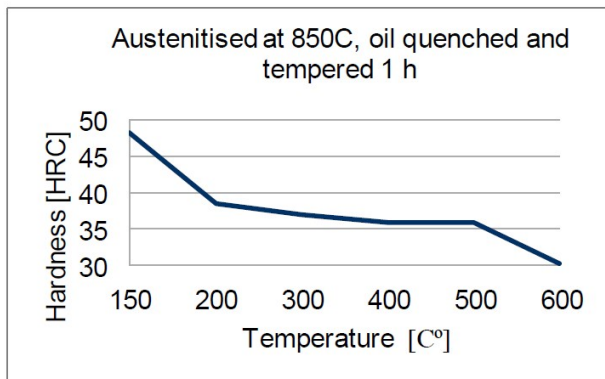

Tempering response after martensitic hardening

Steel cleanliness

Micro inclusions - BQ								Macro inclusions - BQ		
Applied standard	ASTM E45							Applied standard	ISO 3763 (Blue fracture)	
Sampling	ASTM A295							Sampling	Statistical testing on billets.	
Maximum average limits	A		B		C		D		Limits	< 2,5 mm/dm ²
	Th	He	Th	He	Th	He	Th	He		
	2,0	1,5	0,8	0,1	0	0	0,5	0,3		

SUSTAINABILITY-ENVIRONMENTAL IMPACT DATA

At Ovako sustainability and reduction of our environmental impact is a major focus in everything we do.

Further information is found [here](#).

In many international comparisons the crude steel Scope 1-2 emission is a key parameter, ie. the CO₂ emission from the steel works itself.

As of 1 January 2022 we carbon offset all our scope 1 and 2 volume shown below.

Steel works	Hofors	Smedjebacken	Imatra
CO2e/kg	120	62	76

To get the full picture of our products environmental impact we have to look at all of our CO₂ emission sources.

Not only the steel work Scope 1-2 itself, but all operations downstream in our production, heating and heat treatment furnaces etc (full scope 1-2) as well as all the emission from input material, eg. alloys, scope 3.

Steel Grade	Format	Condition ⓘ	Scope 1-3 (CO2e kg /1000 kg steel)	Climate compensated Net emission = Scope 3 (CO2e kg /1000 kg steel) Scope 1 - 2 = 0 (compensated)
821L	Round bar	+SA	612	211
821L	Tube,wall	+SA	633	236

All above data are to be seen as typical values for the specified format and condition. Detailed information about your specific product please contact your sales contact.

Other properties (typical values)

Youngs module (GPa)	Poisson´s ratio (-)	Shear module (GPa)	Density (kg/m3)
210	0.3	80	7800
Average CTE 20-300°C (µm/m°K)	Specific heat capacity 50/100°C (J/kg °K)	Thermal conductivity Ambient temperature (W/m°K)	Electrical resistivity Ambient temperature (µΩm)
12	460 - 480	40 - 45	0.20 - 0.25

Contact us

Would you like to know more about our offers? Don´t hesitate to contact us:

Via e-mail: info@ovako.com

Via telephone: +46 8 622 1300

For more detailed information please visit <http://www.ovako.com/en/Contact-Ovako/>

Disclaimer

The information in this document is for illustrative purposes only. The data and examples are only general recommendations and not a warranty or a guarantee. The suitability of a product for a specific application can be confirmed only by Ovako once given the actual conditions. The purchaser of an Ovako product has the responsibility to ascertain and control the applicability of the products before using them. Continuous development may necessitate changes in technical data without notice. This document is only valid for Ovako material. Other material, covering the same international specifications, does not necessarily comply with the properties presented in this document.